

A novel synthesis of 3,6-bis(2,3-dihydrothieno[3,4-b][1,4]dioxin-5-yl)-9-tosyl-9H-carbazole

Murat ATES*^a, Nesimi ULUDAG^a, Tolga KARAZEHİR^a and Fatih ARICAN^a.

^a Department of Chemistry, Faculty of Arts and Sciences, Namik Kemal University, Degirmenalti Campus, 59030 Tekirdag, Turkey

Abstract 3,6-bis(2,3-dihydrothieno [3,4-b][1,4]dioxin-5-yl)-9-tosyl-9H-carbazole (EDOTTsCz) was synthesized and electrochemically polymerized on glassy carbon electrode (GCE) in 0.1 M tetrabutyl ammonium tetrafluoroborate (NB₄BF₄)/acetonitrile (CH₃CN). Alternating copolymer was formed by CV method. Modified polymer electrode was characterized by Fourier transform Infrared Spectroscopy-Attenuated Transmission Reflectance (FTIR-ATR), Cyclic voltammetry (CV), Scanning electron microscopy-Energy dispersive X-ray analysis (SEM-EDX), Atomic force microscope (AFM) and Electrochemical impedance spectroscopy (EIS). Capacitive behaviors of the modified GCE were defined via Nyquist, Bode-magnitude, Bode-phase and Capacitance plots. A modified copolymer electrode provides enhanced capacitance evaluation, which may results in performance in energy storage devices.

Keywords: Copolymer, Capacitance, Scanning electron microscopy (SEM), Atomic force microscopy (AFM)

1. Introduction

Conducting polymers (CPs) have been an ever developing area in polymer chemistry for four decade [1]. They include an interesting class of materials, which combine some of the mechanical features of plastics with electrical properties typical of metals. The ability to tailor the structure of conjugated polymers allow the rational synthesis of conducting polymers with a broad range of electronic properties since the nature of the repeating units and the functional groups alter the electronic character of polymers [2,3].

3,6-bis(2,3-dihydrothieno [3,4-b][1,4] dioxin-5-yl)-9-tosyl-9H-carbazole monomer was synthesized like in our previous synthesis procedure of 3,6-dibromo-9-tosyl-9H-carbazole [4]. A wide variety of π -conjugated polymers have been synthesized, and characterized in view of their physical and chemical properties. Simple monomers are polymerized with their π -conjugated backbone to form a network of highly delocalized electrons [5]. Electrochemical polymerization technique is more convenient method than chemical method, due to its catalyst-free, one-step conducting film formation, control of film thickness by controlling the deposition charge, etc. [6-9]. Thus, the polymers were coated on the

electrode surface and show good electroactivity [10-13].

The most widely studied electrochemically conducting polymers (CPs) can be divided four major classes: polypyrroles, polyanilines, polycarbazoles and polythiophenes [14-17]. They can be made into a wide variety of morphologies [18, 19] and used in a wide variety of applications, such as biosensor [20], solar cell [21], supercapacitor [22, 23], etc. In the class of conducting polymers with a π -conjugated backbone, polythiophenes are particularly interesting due to their good thermal and electrical properties, good stability and functionalization [24]. Chemical functionalization, in principle, allows for fine-tuning of polymers physical and electronic properties [25-27]. Poly(3,4-ethylenedioxythiophene) (PEDOT) is a thiophene derivative, exhibits many favorable properties, such as a low band gap (1.6 eV), a high lying HOMO, an easy conversion into the conducting state and a high stability in the conducting form. However, the poor solubility of PEDOT is a strong drawback for further applications in electrical and optical devices [28]. Compared to other unsubstituted polythiophene and its derivatives, PEDOT exhibits a distinctly low oxidation potential and a small band gap in the

oxidized state [29, 30]. Carbazole and its derivatives have been known for many years to exhibit excellent electro-active and photoactive properties due to their high hole-transporting mobility of the charge carriers [31-35], good environmental stability and photo-conductivities [36, 37].

Their electroluminescence is a result of the large enough band gap of the biphenyl unit. These properties are especially valuable for new polymeric materials, when these compounds are used as monomers in syntheses of polymer [38, 39].

Many potential applications of conducting polymers become limited because of their general insolubility in common organic solvents, poor mechanical properties and their insufficient environmental stability. To improve these properties, an electrochemical method was used to prepare copolymers with other monomers [40]. Electrochemical synthesis of copolymers is a good strategy in new electrically active materials that combine the properties of the constituent homopolymers [41-43]. Moreover, more and more new derivatives of the common CPs, novel CPs, or their copolymers with good fluorescence property, high electrical conductivity, satisfied thermal stability, or other properties, have been developed in literature [44].

Electrochemical impedance spectroscopy (EIS) allows the analysis of the properties of materials and systems by applying them alternate electric signals of different frequencies (voltage or current) and measuring the corresponding electric output signals (current or voltage) [45-52]. These signals can be applied in a broad frequency range, which makes it possible to cover a wide range of time constants. Moreover, EIS has been highlighted as a technique that is suitable to study the interfacial process [53, 54].

As a result, EDOTTsCz was electropolymerized on GCE and CFME. Polymer characterization was done by CV, FTIR-ATR, SEM-EDX, AFM and EIS analysis.

2. Experimental

2.1. Materials

All chemicals were used as received from Aldrich Chemical without further purification. Alumina polishing suspension (Balkowski

International Corporation, 0.05 CB micron Gamma Type, CR85S), Carbon fiber microelectrode (SGL SIGRAFIL C 320 B) and Carbon cement (LEIT-C-Plast) were used in the electropolymerization experiments.

2.2. Instrumentation

Cyclic voltammetry (CV) was performed using PARSTAT 2273 (software: powersuit and Faraday cage: BASI Cell Stand C3) in a three electrode configuration, which employing GCE (area: 0.07 cm²) and CFME (area: 0.022 cm²) as the working electrode, platinum wire as the counter electrode and Ag/AgCl as the reference electrode.

Modified electrodes were characterized by FTIR-ATR spectroscopy (Perkin Elmer, Spectrum One B, with an universal ATR attachment with a diamond and ZnSe crystal). Electrocoated copolymers were analyzed by Scanning electron microscopy (SEM) and Energy Dispersive X-ray analysis (EDX) using a Carl Zeiss Leo 1430 VP. Average values of the increase in thickness were obtained from SEM images taking into account the diameter of the uncoated CFME. The AFM images were obtained with Park System XE 100. In all AFM analysis, the non-contact mode was employed by using Al coated high resonance frequency silicon tips (265-400 kHz) with 4 μm thickness, 35 μm mean width, 125 μm length and 20-75 N/m force constant. High resolution images (1024x1024 pixels) and the raw data collected by the XEI image processing and analysis using left shadowing.

2.3. Electrochemical impedance spectroscopic measurements

The electrochemical impedance spectroscopic (EIS) measurements were taken in 0.1 M tetrabutyl ammonium tetrafluoroborate (NB₄BF₄) / acetonitrile (CH₃CN). EIS measurements were performed in monomer free electrolyte solution with a perturbation amplitude 10 mV over a frequency range of 10 mHz to 100 kHz with PARSTAT 2273.

3. Results and Discussions

3.1. Synthesis of EDOTTsCz monomer

2,3-dihydrothieno[3,4-b][1,4]dioxin substance (40.8 mmole) dissolves in 100 mL THF under nitrogen atmosphere and mixes by stirrer. Mixture

condenses to $-70\text{ }^{\circ}\text{C}$ with acetone-liquid nitrogen mixture. After mixing ~ 30 minutes, *n*-butyl lithium (39 mmole) was added by injection method via syringe. After 1 h, mixture temperature adjusted to $0\text{ }^{\circ}\text{C}$, and $\text{MgBr}_2 \cdot \text{Et}_2\text{O}$ substance (42 mmole) was added to the mixture. 1 h later, 3,6-dibromo-9-tosyl-9*H*-carbazole (6.3 mmole) and NiCl_2 (0.92 mmole) dissolves in 30 ml THF and added to the mixture. Mixture was adjusted to the room temperature and mixes for 60 h at room temperature. Organic phase rinsed with 10 % NaOH and removes the organic phase from the mixture. Solvent removes from mixture by the help of rotary evaporator. Silica gel chromatography was evaluated with dichloromethane and crystallized with diethylether. The physical properties of substance are given as the following; Rf: 0.80 (*n*-hexan-dichloromethane 1:1), melting point: $187\text{ }^{\circ}\text{C}$ (yield: 60 %).

FT-IR (KBr): $2960\text{--}2877\text{ cm}^{-1}$ (C-H aromatic), 1589 cm^{-1} (C=C, aromatic), 1171 cm^{-1} (S=O).

$^1\text{H-NMR}$ (CDCl_3): δ 8.34-8.31 (dd, 2H, aromatic CH), 7.9 (dd, 2H, aromatic CH), 7.7 (dd, 2H, aromatic CH), 7.5 (m, 2H, aromatic CH), 7.4-7.3 (m, H, aromatic CH), 7.25 (s, H, aromatic CH), 7.1 (dd, 2H, aromatic CH), 3.5 (m, 2H, CH_2), 3.3 (m, 2H, CH_2), 2.31 (s, 3H, CH_3).

$^{13}\text{C-NMR}$ (CDCl_3): δ 144 (CH), 138 (CH), 134 (CH), 129 (CH), 128 (CH), 127 (CH), 126 (CH), 126.37 (CH), 126.11 (CH), 123 (CH), 119 (C), 115 (C), 77.34 (CH_2), 77.22 (CH_2), 77.02 (CH_2), 76.70 (CH_2), 58.82 (CH), 24 (CH), 21.40 (CH), 21.20 (CH), 19.72 (CH), 13.67 (CH_3).

A novel synthesized monomer structure was given in **Fig.1**. EDOTsCz was electropolymerized on CFME in $0.1\text{ M NaClO}_4 / \text{CH}_3\text{CN}$ by CV method. Polymerization was done at a scan rate of 100 mVs^{-1} , potential range: $0.5\text{--}1.6\text{ V}$ (**Fig. 2**). By increasing the initial monomer concentration ($[\text{EDOTsCz}]_0$) from 1 mM ($Q_a = 0.447\text{ mC}$) to 10 mM ($Q_d = 15.3\text{ mC}$), total charges increases by electrogrowth process. New substrate surface occurs by electrogrowth process of every cycle on the surface. Thickness of electrode, chain length of copolymer and also current density increase by addition of monomer during electrogrowth process.

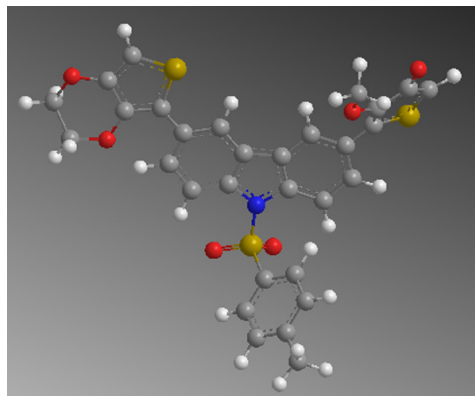


Fig. 1. 3 dimensional structure of 3,6-bis(2,3-dihydrothieno[3,4-b][1,4]dioxin-5-yl)-9-tosyl-9*H* carbazole.

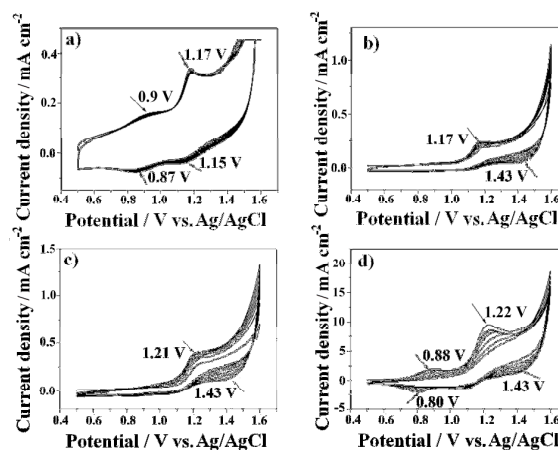


Fig. 2. Electro-growth of 3,6-bis(2,3-dihydrothieno[3,4-b][1,4]dioxin-5-yl)-9-tosyl-9*H*-carbazole on CFME, **a**) $[\text{EDOTsCz}]_0 = 1\text{ mM}$ ($Q_a = 0.447\text{ mC}$); **b**) $[\text{EDOTsCz}]_0 = 3\text{ mM}$ ($Q_b = 2.42\text{ mC}$); **c**) $[\text{EDOTsCz}]_0 = 5\text{ mM}$ ($Q_c = 9.064\text{ mC}$); **d**) $[\text{EDOTsCz}]_0 = 10\text{ mM}$ ($Q_d = 15.3\text{ mC}$), 8th cycle, Scan rate: 100 mV s^{-1} , $0.1\text{ M NaClO}_4 / \text{CH}_3\text{CN}$, Potential range: $0.5\text{--}1.6\text{ V}$.

Oxidation peak potentials of poly(EDOTsCz) were obtained as 1.17 V , for $[\text{EDOTsCz}]_0 = 1\text{ mM}$ and $[\text{EDOTsCz}]_0 = 3\text{ mM}$. By increasing of the initial monomer concentration from 5 mM to 10 mM , the oxidation peak potentials increase from 1.21 V to 1.22 V . This is expected due to formation of more bulky structure.

3.1. Electropolymerization of EDOTsCz on GCE in $\text{NBu}_4\text{BF}_4 / \text{CH}_3\text{CN}$

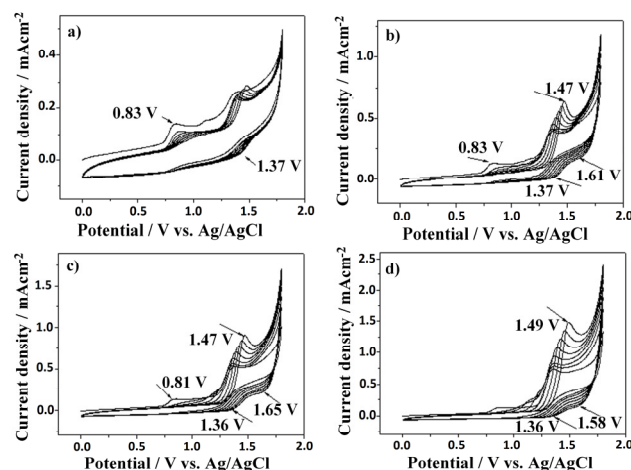


Fig. 3. Electrogrowth of 3,6-bis(2,3-dihydrothieno[3,4-b][1,4]dioxin-5-yl)-9-tosyl-9H-carbazole on GCE, **a)** $[\text{EDOTsCz}]_0 = 1 \text{ mM}$ ($Q_a = 1.217 \text{ mC}$); **b)** $[\text{EDOTsCz}]_0 = 3 \text{ mM}$ ($Q_b = 2.127 \text{ mC}$); **c)** $[\text{EDOTsCz}]_0 = 5 \text{ mM}$ ($Q_c = 2.931 \text{ mC}$); **d)** $[\text{EDOTsCz}]_0 = 10 \text{ mM}$ ($Q_d = 4.054 \text{ mC}$), 8 cycle was taken for electrogrowth process. Scan rate: 100 mV s^{-1} , $0.1 \text{ M NBu}_4\text{BF}_4 / \text{CH}_3\text{CN}$, Potential range: $0.0 - 1.8 \text{ V}$.

Peak potentials were obtained as $\sim 0.83 \text{ V}$ and $\sim 1.37 \text{ V}$, respectively. There is no higher shift by addition of monomer concentration. However, current density increases higher amount from 0.1 mA cm^{-2} to 1.5 mA cm^{-2} by addition of $[\text{EDOTsCz}]_0 = 1 \text{ mM}$ to $[\text{EDOTsCz}]_0 = 10 \text{ mM}$ (**Fig.3**). In literature, poly(3,6-bis-(2-(3,4-ethylenedioxy)thienyl)-*N*-dodecylcarbazole) obtained by anodic coupling of 3,6-bis(2-(3,4-ethylenedioxy)-thienyl)-*N*-dodecylcarbazole in acetonitrile and the investigation of its in situ conductivity and in situ ESR behavior [55]. The polythiophene oxidation of literature is given by concern of paramagnetic polarons and diamagnetic bipolarons [56, 57]. These species are polymeric analogs cation radicals and dications. It has been proposed that oxidation leads first to polarons, and as the extent of oxidation increases along one chain, these polarons combine to form bipolarons.

3.2. Plot of anodic and cathodic peak current density vs. scan rate and square root of scan rate

dependence of Poly(EDOTsCz) / GCE in monomer-free electrolyte

When inspected the plot of Poly(EDOTsCz) modified GCE anodic and cathodic peak current density vs. scan rate and square root of scan rate dependence in monomer free solution in $0.1 \text{ NBu}_4\text{BF}_4 / \text{CH}_3\text{CN}$, regression coefficient (R) for $[\text{EDOTsCz}]_0 = 1$ and 10 mM , respectively. The electrochemical process where diffusion controlled process applies for $[\text{EDOTsCz}]_0 = 3$ and 5 mM , respectively. It might also be an indication of thin film formation (**Table 1**).

Table 1. According to initial monomer concentration, scan rate and square root of scan rate change with regression coefficient.

Current density ($i_p / \text{mA cm}^{-2}$) can be calculated for reversible system from Randles-Sevcik equation: $i_p = (2.69 \times 10^5) \times A \times D^{1/2} \times C_0 \times v^{1/2}$ (where v is the scan rate, A is electrode area, D is the diffusion

Initial monomer concentration	Regression Coefficient (R)			
	Scan Rate-Current density		Square root of scan rate-Current density	
	Anodic	Cathodic	Anodic	Cathodic
1	0.9879	-0.9816	0.9976	-0.9988
3	0.9963	-0.9905	0.9929	-0.9427
5	0.9982	-0.9961	0.9892	-0.9607
10	0.9857	-0.9790	0.9982	-0.9951

coefficient of electro-active species in the solution). If peak current is proportional to v where thin film formation [58, 59]. If the peak current is proportional to $v^{1/2}$ in the range of scan rate, where diffusion control applies [60]. Diffusion coefficient (D) was obtained as 1.35×10^{-15} for $[\text{EDOTsCz}]_0 = 1 \text{ mM}$, $D = 6.14 \times 10^{-16}$ for $[\text{EDOTsCz}]_0 = 3 \text{ mM}$, $D = 4.97 \times 10^{-16}$ for $[\text{EDOTsCz}]_0 = 5 \text{ mM}$ and $D = 1.14 \times 10^{-17}$ for $[\text{EDOTsCz}]_0 = 10 \text{ mM}$ (**Fig.4**).

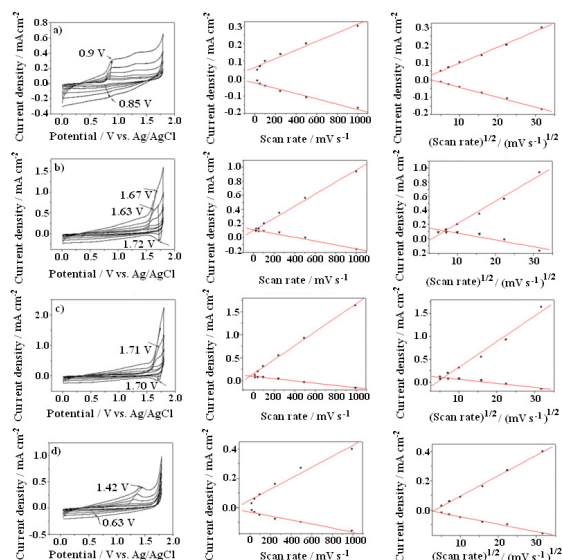


Fig. 4 Plot of anodic and cathodic peak current density vs. scan rate and square root of scan rate dependence of Poly(EDOTsCz) / GCE in monomer free solution in 0.1 $\text{NB}_4\text{BF}_4 / \text{CH}_3\text{N}$, potential range: 0.5 V-1.6V scan rate: 25,50, 100, 250, 500, 1000 mVs^{-1} a) [EDOTsCz] $_0$ = 1 mM, b) [EDOTsCz] $_0$ = 3 mM c) [EDOTsCz] $_0$ = 5 mM, d) [EDOTsCz] $_0$ = 10 mM.

Electrochemical impedance spectroscopic results of Poly(EDOTsCz) / GCE in $\text{NaClO}_4 / \text{CH}_3\text{CN}$

When inspected, Nyquist plot of Poly(EDOTsCz)/GCE, low frequency capacitances (C_{LF}) were obtained as: $C_{\text{LF}} = 2.1 \text{ mF cm}^{-2}$ for [EDOTsCz] $_0$ = 1 mM, $C_{\text{LF}} = 2.55 \text{ mF cm}^{-2}$ for [EDOTsCz] $_0$ = 3 mM, $C_{\text{LF}} = 2.62 \text{ mF cm}^{-2}$ for [EDOTsCz] $_0$ = 5 mM and $C_{\text{LF}} = 2.41 \text{ mF cm}^{-2}$ for [EDOTsCz] $_0$ = 10 mM as given **Fig. 5**. The highest capacitance value, $C_{\text{LF}} = 2.62 \text{ mF cm}^{-2}$ was obtained for [EDOTsCz] $_0$ = 5 mM.

Electrochemical impedance spectroscopy can be used to identify subtle changes on surface of polymer modified electrode [61]. Ac impedance spectroscopy is given as a result of specific power potential of electrochemical capacitor and combination of resistance [62].

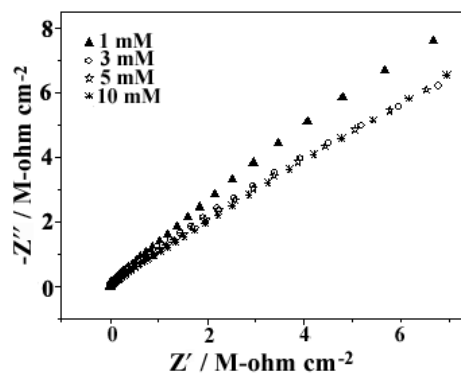


Fig. 5. Nyquist plot for Poly(EDOTsCz) electrocoated on GCE, [EDOTsCz] $_0$ = 1, 3, 5 and 10 mM in 0.1 M $\text{NaClO}_4 / \text{CH}_3\text{CN}$.

One important point in electrochemical impedance spectroscopy is the process of moving into electrode constitution with the resistances [63].

In our previous study, we have studied 9-tosyl-9H-carbazole for [EDOTsCz] $_0$ = 1, 3, 5 and 10 mM in 0.1 M $\text{NaClO}_4 / \text{CH}_3\text{CN}$. As a result of equivalent circuit models of R(CR)(QR)(CR), the highest C_{LF} value was obtained at the frequency of 0.01 Hz in initial monomer concentration of 10 mM as 50 mF cm^{-2} [64].

A value of double layer capacitance (C_{dl}) can be calculated from a Bode-magnitude plot, by extrapolating the linear section to value ω ($\log \omega = 0$), the relationship $|Z| = 1 / C_{\text{dl}}$, as shown in **Fig. 6**.

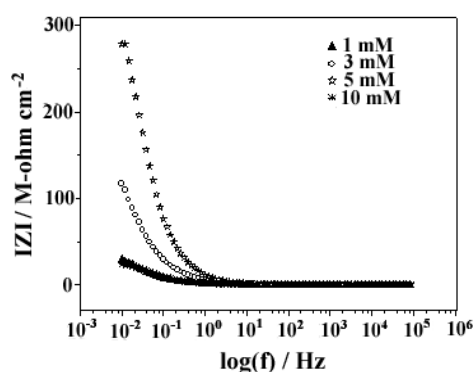


Fig. 6. Bode-magnitude plot of Poly(EDOTsCz) electrocoated on GCE, [EDOTsCz] $_0$ = 1, 3, 5 and 10 mM in 0.1 M $\text{NaClO}_4 / \text{CH}_3\text{CN}$.

C_{dl} was obtained from Bode-magnitude plot as $\sim 1.66 \text{ mF cm}^{-2}$ for $[\text{EDOTTsCz}]_0 = 1, 3, 5$ and 10 mM (Fig. 6).

Comparison of FTIR-ATR spectrum of EDOTTsCz and Poly(EDOTTsCz)

When examining FTIR-ATR spectrum of EDOTTsCz and polymer, some of peaks were shifted associated with polymer formation. For example, the peaks at 2960 and 2877 cm^{-1} correspond to C-H stretching, at 1589 cm^{-1} attributed to C=C stretching, and at 1171 cm^{-1} belongs to S=O (Fig. 7).

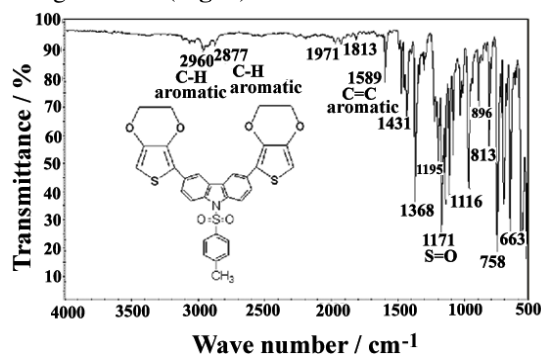


Fig. 7. FTIR-ATR spectrum of EDOTTsCz.

In FTIR-ATR spectrum of poly(EDOTTsCz) correspond to peak at 3585 cm^{-1} for C-H stretching, at 1624 cm^{-1} for C=C stretching, at 1431 cm^{-1} for CH_3 , at 1369 cm^{-1} for C-O stretching, at 1096 cm^{-1} for dopant ion (ClO_4^-) and at 755 cm^{-1} for C-S stretching (Fig. 8).

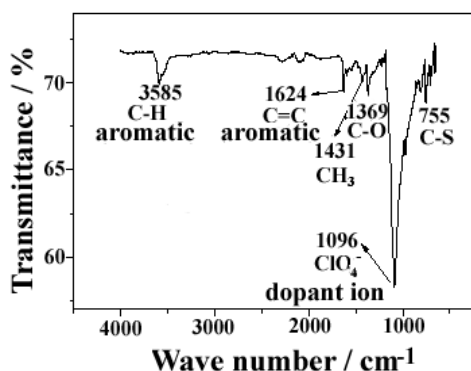


Fig. 8. FTIR-ATR spectrum of Poly(EDOTTsCz)/CFME, $[\text{EDOTTsCz}]_0 = 10 \text{ mM}$,

chronoamperometric method, 300 s , constant potential of 1.6 V in $0.1 \text{ M NaClO}_4 / \text{CH}_3\text{CN}$.

SEM-EDX Analysis

SEM image of Poly(EDOTTsCz) / CFME shows a homogeneous film (Fig. 9). EDX data was given in Fig.10 and Table 2.

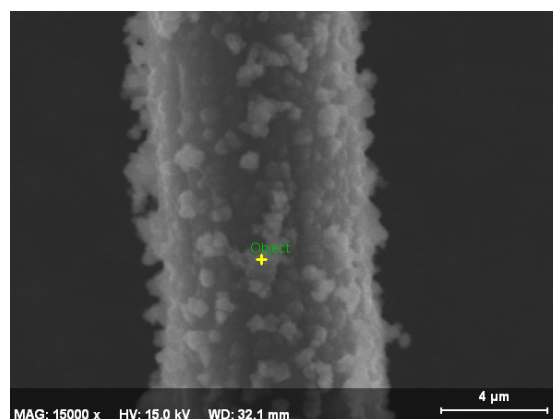


Fig. 9. SEM-EDX point analysis of Poly(EDOTTsCz), $[\text{EDOTTsCz}]_0 = 10 \text{ mM}$ ($Q_d = 15.3 \text{ mC}$). Electrogrowth process was taken 8 cycle, scan rate: 100 mV s^{-1} , potential range: $0.5\text{-}1.6$ in $0.1 \text{ M NaClO}_4 / \text{CH}_3\text{CN}$.

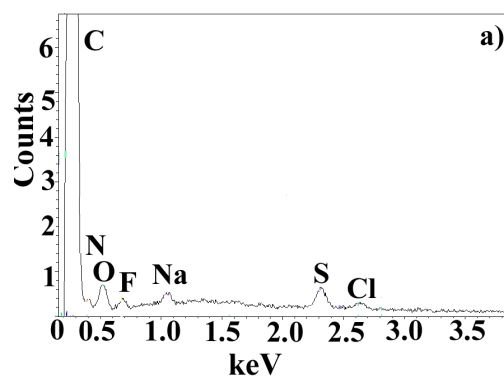


Fig.10. EDX point analysis of Poly(EDOTTsCz) $[\text{EDOTTsCz}]_0 = 10 \text{ mM}$ ($Q_d = 15.3 \text{ mC}$). Electrogrowth process was taken 8 cycle, scan rate: 100 mV s^{-1} , potential range: $0.5\text{-}1.6$ in $0.1 \text{ M NaClO}_4 / \text{CH}_3\text{CN}$.

Table 2. EDX point analysis of Poly(EDOTTsCz)

Elements	Point Analysis
	Weight / %
Carbon	56.80
Nitrogen	16.44
Oxygen	16.48
Fluorine	7.02
Sodium	2.27
Sulphur	0.68
Chlorine	0.31

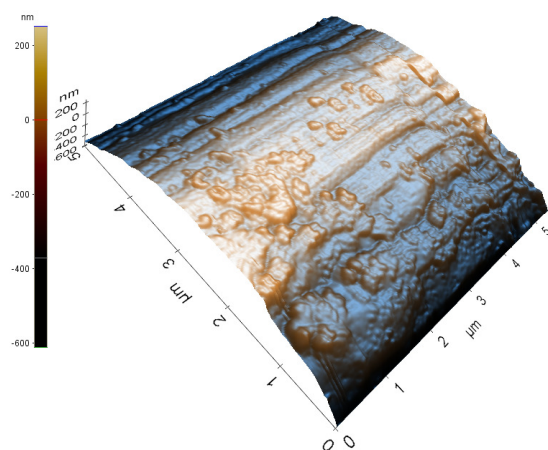
AFM Analysis

Fig. 11. AFM images of poly(EDOTTsCz) coated on CFME with scan size of $5\mu\text{m} \times 5\mu\text{m}$, scan rate: 1 Hz, $[\text{EDOTTsCz}]_0 = 10 \text{ mM}$ ($Q_d = 15.3 \text{ mC}$). Electropolymerization process was taken 8 cycle, scan rate: 100 mV s^{-1} , potential range: 0.5-1.6 in 0.1 M $\text{NaClO}_4 / \text{CH}_3\text{CN}$.

AFM images of poly(EDOTTsCz) shows the coating process by observing granules on CFME (**Fig.11**).

4. Conclusions

Conducting polymers have been used in energy storage devices due to their charge-discharge capability [65, 66]. Doping and de-doping process supplies the possibility of capacitor behavior (pseudocapacitance) for conducting polymers [67]. In this study, a new π conjugated substance was chemically synthesized and characterized by FTIR, $^1\text{H-NMR}$, and $^{13}\text{C-NMR}$ spectroscopy. EDOTTsCz

monomer was electrochemically polymerized on GCE and CFME in 0.1 M $\text{NaClO}_4 / \text{CH}_3\text{CN}$ and $\text{NB}_4\text{BF}_4/\text{CH}_3\text{CN}$, respectively. Modified copolymer was characterized by CV, FTIR-ATR, SEM-EDX, EIS, and AFM, respectively. In future, polymer may also be used as capacitor properties in energy storage devices. High power density and long stability may be supplied by using graphite anode electrode, carbon nanotube, and composite materials [68, 69].

5. Acknowledgments

The support of the TUBITAK (Scientific and Technological Research Council of Turkey) (110T791) is gratefully acknowledged. We also thank to Serhat Tıkız (Afyon Kocatepe University, Technology and Research Center, (TUAM), Afyon, Turkey) and Yakup Bakis (Fatih University, BINATAM, Istanbul, Turkey) for recording SEM-EDX and AFM images, respectively.

6. References

- * E-mail address: mates@nku.edu.tr
- [1]. G.G. Wallace, G.M. Spinks, L.A.P. Kane-Maguire and P.R. Teasdale, *Conductive Electroactive Polymers: Intelligent Materials Systems*, 2nd ed., CRC, London, 2003.
 - [2]. J.R. Reynolds, A. Kumar, J.L. Reddinger, B. Sankaran, S.A. Saap and G.A. Sotzing, *Synthetic Metals*, **85**, 1295 (1997).
 - [3]. S. Sezgin, M. Ates, E.A. Parlak and A.S. Sarac, *Int. J. Electrochem. Sci.*, **7**, 1093 (2012).
 - [4]. M. Ates, N. Uludag and A.S. Sarac, *Fibers and Polymers*, **12(1)** 8 (2011).
 - [5]. K.I. Aly, *Journal of Applied Polymer Science*, **123**, 3390 (2012) S.Dobrinias, Doctoral thesis, The University of Bucharest, 2002.
 - [6]. B.L. Groenendaal, F. Jonas and D. Freitag, *Adv Mater*, **12**, 481 (2000).
 - [7]. RD. Mcculloch, *Adv Mater*, **10**, 93 (1998).
 - [8]. L.G. Groenendaal, P.H. Zotti and S.M. Aubert, *Adv Mater*, **15**, 855 (2003).
 - [9]. X. Wang, R. Yue, B. Lu, Z. Wei and J. Xu, *J. Mater Sci*, **45**, 1963 (2010).
 - [10]. P.M. Beaujuge, S. Ellinger and J.R. Reynolds, *Nat. Mater.*, **7**, 795 (2008).

- [11]. C.H. Chang, K.L. Wang, J.C. Jiang, D.J. Liawa, K.R. Lee, J.Y. Lai and K.H. Lai, *Polymer*, **51**, 4493 (2010).
- [12]. S.H. Cheng, S.H. Hsiao, T.H. Su and G.S. Liou, *Polymer*, **46**, 5939 (2005).
- [13]. H. Goto, *Journal of Polymer Science Part A: Polymer Chemistry*, **50**, 622 (2012).
- [14]. M. Deng, X. Yang, M. Silke, W. Qiu, M. Xu and G. Borghs, H. Chen, **158**, 176 (2011).
- [15]. J. Li, H. Xie, Y. Li, J. Liu and Z. Li, *Journal of Power Sources*, **196**, 10775 (2011).
- [16]. B. Senthilkumar, P. Thenamirtham and R.K. Selvan, *Applied Surface Science*, **257**, 9063 (2011).
- [17]. M. Łapkowski, P. Data, A.N. Oleksy, J. Sołoducho, S. Roszak, *Materials Chemistry and Physics*, **131**, 757 (2012).
- [18]. M.J. Antony and M. Jayakannan, *Journal of Physical Chemistry B*, **114**, 1314 (2010).
- [19]. S.V. Kasisomayajula, X. Qi, C. Vetter, K. Croes, D. Pavlacky and V.J. Gelling, *Journal of Coatings Technology and Research*, **7**, 145 (2010).
- [20]. I. Cesarino, F. C. Moraes and S.A.S. Machado, *Electroanalysis*, **23**, 2586 (2011).
- [21]. S.K. Swathi, K. Ranjith, P. Kumar and P.C. Ramamurthy, *Solar Energy Materials & Solar Cells*, **96**, 101 (2012).
- [22]. M. Jin, G. Han, Y. Chang, H. Zhao and H. Zhang, *Electrochimica Acta*, **56**, 9838 (2011).
- [23]. J.B. Spires, H. Peng, D. Williams and J.T. Sejdic, *Electrochimica Acta*, **58**, 134 (2011).
- [24]. Y. Pang, X. Li, H. Ding, G. Shi and L. Jin, *Electrochim. Acta*, **52**, 6172 (2007).
- [25]. J. Hou, L. Huo, C. He, C. Yang and Y. Li, *Macromolecules*, **39**, 594 (2006).
- [26]. F. Liesa, C. Ocampo, C. Alemán, E. Armelin and R. Oliver, *J. Appl. Polym. Sci.*, **102**, 1592 (2006).
- [27]. M.R.A. Alves, H.D.R. Calado, C.L. Donnici and T. Matencio, *Synthetic Metals*, **160**, 22 (2010).
- [28]. L. Miozzo, N. Battaglini, D. Braga, L.Kergoat, C. Suspene and A. Yassar, *Journal of Polymer Science Part A: Polymer Chemistry*, **50**, 534 (2012).
- [29]. M. Dietrich, J. Heinze, G. Heywang and F. Jonas, *J. Electroanal Chem*, **369**, 87, (1994).
- [30]. J.H. Chen, C.A. Dai and W.Y. Chiu, *Journal of Polymer Science: Part A: Polymer Chemistry*, **46**, 1662 (2008).
- [31]. E. Cloutet, P. Yammine, D. Ades and A. Siove, *Synth Met.*, **102**, 1302 (1999).
- [32]. R. Dale, R. Meyer, N. Jubran, Z. Tokarski, R. Moudry and K. Law, *J. Electroanal. Chem.*, **567**, 19 (2004).
- [33]. J.F. Morin, M. Leclerc, D. Ades and A. siove, *Macromol. Rapid Commun.*, **26**, 761 (2005).
- [34]. H.C. Lin, C.M. Tsai, J.T. Lin and K.R.J. Thomas, *Synth. Met.*, **156**, 1155 (2006).
- [35]. R. Yue, S. Chen, C. Liu, B. Lu, J. Xu, J. Wang and G. Liu, *J. Solid State Electrochem.*, **16**, 117 (2012).
- [36]. J. Wang, B. Lu, C. Liu, J. Xu and M. Pei, *J. Mater Sci.*, **45**, 5769 (2010).
- [37]. J. Wang, B. Lu, C. Liu, J. Xu and M. Pei, *J. Mater Sci.*, **45**, 5769 (2010).
- [38]. E. Clouter, C. Olivero, D. Ades, C. Castex and A. Siove, *Polymer*, **43**, 3489 (2002).
- [39]. M. Lapkowski, J. Zak, K. Karon, B. Marciniec and W. Prukala, *Electrochimica Acta*, **56**, 4105 (2011).
- [40]. V. Raj, D. Madheswari, and M.M. Ali, *Journal of Applied Polymer Science*, **119**, 2824 (2011).
- [41]. J. Xu, G. Nie, S. Zhang, X. Han, J. Hou and S. Pu, *J. Mater. Sci.*, **40**, 2867 (2005).
- [42]. G. Beggiato, G. Casalbore-Miceli, A. Geri, A. Berlin and G. Pagani, *Synth. Met.*, **82**, 11 (1996).
- [43]. A.F. Morgera, C.D. Casa, P.C. Bizzarri, M. Lanzi and A. Missiroli, *Macromolecules*, **38**, 3170 (2005).
- [44]. Q. Hao, X. Xie, W. Lei, M. Xia, F. Wang, and X. Wang, *J. Phys. Chem. C*, **114**, 9608 (2010).
- [45]. A. Bard and, R. Faulkner., *Electrochemical methods: Fundamentals and applications*, ed. John Wiley & Sons Inc., New York, 2001.
- [46]. E. Barsoukov and J.R. Macdonald, *Impedance spectroscopy: Theory, experiment, and applications*, 2nd ed.. John Wiley & Sons Inc., New York, 2001.
- [47]. R.H. Labrador, R. Masot, M. Alcañiz, D. Baigts, J. Soto, R. Martínez-Mañez, E. García-Breijó, L. Gil and J.M. Barat, *Food Chemistry*, **122**, 864 (2010).
- [48]. Y. Hou, S. Helali, A. Zhang, N. Jaffrezic-Renault, C. Martelet, J. Minic, T. Gorojankina,

- M.A. Persuy, E. Pajot-Augy, R. Salesse, F. Bessueille, J. Samitier, A. Errachid, V. Akimov, L. Reggiani, C. Pennetta, and E. Alfinito, *Biosens Bioelectron.*, **21**, 1393 (2006).
- [49]. G. Liu, J. Wang, J. Kim, M.R. Jan and G. E. Collins, *Anal. Chem.*, **76**, 7126 (2004).
- [50]. O.A. Loaiza, P.J. Lamas-Ardisana, E. Jubete, E. Ochoteco, I. Loinaz, G. Cabanero, I. García and S. Penades, *Anal. Chem.*, **83**, 2987 (2011).
- [51]. A. Manickam, A. Chevalier, M. McDermott, A.D. Ellington, and A. Hassibi, *IEEE Transactions on Biomedical Circuits and Systems*, **4**, 6 (2010).
- [52]. C.F. Sanchez, C.J. McNeil and K. Rawson, *Trends in Analytical Chemistry*, **24**, 1, (2005).
- [53]. J. R. Scully, D. C. Silverman and M.W. Kendig, *Electrochemical Impedance: Analysis and Interpretation*, ASTM: Philadelphia, 1993.
- [54]. F. R. Simoes, L. A. Pocrifka, L. F. Q. P. Marchesi, and E. C. Pereira, *J. Phys. Chem. B*, **115**, 11092 (2011).
- [55]. G. Zotti, G. Schiavon, S. Zecchin and L. Groenendaal, *Chem. Mater.*, **11**, 3624 (1999).
- [56]. M. Scharli, K.W. Kiess, G. Harbeke, W. Berlinger, K.W. Blazey, K.A. Muller, *Synth. Met.*, **22**, 317 (1988).
- [57]. P.A. Cristensen, A. Hamnett, A.R. Hillman, M.J. Swann, S.J. Higgins, *J. Chem. Soc. Faraday Trans.*, **88**, 595 (1992).
- [58]. A.S. Sarac, E. Dogru, M. Ates and E.A. Parlak, *Turk J. Chem*, **30**, 401 (2006).
- [59]. M. Ates, N. Uludag and A.S. Sarac, *Materials Chemistry and Physics*, **127**, 120 (2011).
- [60]. J.F. Rusling and S.L. Suib, *Adv. Mater.*, **6**, 92 (1994).
- [61]. W.C. Chen, T.C. Wen and A. Gopalan, *Synth.Met.*, **128**, 179 (2002).
- [62]. A. Techagumpuch, H.S. Nalwa and S. Miyata, *Electroresponsive Molecular and Polymer Systems*, in: Skothein T.A. ed. Marcel Dekker, New York, 1991.
- [63]. A. Rudge, J. Davey, I. Raistrick, S. Gottesfeld and J.P. Ferraris, *J.Power Sources*, **47**, 89 (1994).
- [64]. M. Ates, N. Uludag and A.S. Sarac, *Fibers and Polymers*, **12**, 8 (2011).
- [65]. D. Fateaux and R. Koksang, *J. Appl.Electrochem.*, **23**, 1 (1993).
- [66]. T.A. Scotheim, R.L. Elsenbaumer and J.R. Reynolds, *Handbook of Conducting Polymers*, 2nded. Marcel Dekker, New York, 1998.
- [67]. J.O. Iroh and K. Levine, *J.Power Sources*, **117**, 267 (2003).
- [68]. R. Xu, J.R. Li, A. Tan, Z.L. Tang, Z.T. Zhang, *J.Power Sources*, **196**, 2283 (2011).
- [69]. G.Q. Liua, L. Wen, G.Y. Liu, Q.Y. Wu, H.Z. Luo, B.Y. Ma and Y.W. Tian, *J. Alloys Compd.*, **509**, 6427 (2011).

Submitted: March 10th 2012

Accepted in revised form: April 30th 2012